

RESEARCH ARTICLE

Entrapment of protease from *Bacillus* sp. in polyvinyl alcohol hydrogels

Fatih Mehmet Hasbek^{1*}  | Deniz Yildirim² ¹ University of Cukurova, Institute of Natural and Applied Science, Department of Biotechnology, Adana, Türkiye² University of Cukurova, Faculty of Ceyhan Engineering, Department of Chemical Engineering, Adana, Türkiye*Corresponding author: E-mail: dyildirim@cu.edu.tr; Ph.: +903226137311; Fax: +90322 613 5180

Citation: Hasbek, F.M., & Yildirim, D. (2025). Entrapment of protease from *Bacillus* sp. in polyvinyl alcohol hydrogels. The European chemistry and biotechnology journal, 3, 21-31.

<https://doi.org/10.62063/ecb-38>

License: This article is licensed under a Creative Commons Attribution-NonCommercial 4.0 International License (CC BY-NC 4.0).

Peer review: Externally peer reviewed.

Received: 08.10.2024

Accepted: 08.11.2024

Online first: 15.11.2024



Abstract

This study highlights the effective immobilization of protease from *Bacillus* sp. in polyvinyl alcohol hydrogels and its characterization. Both free and entrapped proteases exhibited optimal activity at pH 8.0 and 55°C, indicating that the immobilization did not significantly alter the enzyme's fundamental properties. The entrapment in polyvinyl alcohol hydrogels significantly enhanced thermal stability. After 24 hours at 55°C, the free protease retained only 19% of its initial activity, whereas the entrapped protease retained 72%. The entrapped protease showed a longer half-life of 53.3 hours compared to 10.6 hours for the free protease. The K_m and V_{max} values of free protease were determined to be 0.5 mg/mL and 23.3 U/mg protein, respectively, for casein. These values were found to be 0.2 mg/mL and 23.8 U/mg protein, respectively for the entrapped protease. The entrapped protease retained 58% of its initial activity after 5 reuses in a batch reactor. As a result, the entrapment of *Bacillus* sp. protease in polyvinyl alcohol is an effective immobilization method due to its simplicity, low cost, and ability to provide a 5-fold increase in thermal stability.

Keywords: *Bacillus* sp., immobilization, polyvinyl alcohol, protease



Introduction

Proteases are used in various industrial fields, such as detergents, pharmaceuticals and medicine, occupying 60% of the worldwide enzyme market (Dyer & Weiss, 2022). Proteases catalyze the hydrolysis of peptide bonds, and the hydrolyzates obtained are used in the cosmetic, food and pharmaceutical industries owing to their antioxidant, antihypertensive, antidiabetic, and antimicrobial activities (Brandelli & Daroit, 2024; Elbira et al., 2024; Sun et al., 2024). Therefore, chemical, physical and enzymatic methods have been used to obtain protein hydrolyzates from different sources (Tang et al., 2023). Due to their low cost, safety and environmentally friendly nature, enzymatic methods are preferred over chemical and physical methods (Sun et al., 2024). However, the recovery problem of soluble enzymes from reaction medium, contamination of the final product with enzyme molecules as well as stability problems in organic solvents and/or at extreme pHs and temperatures make soluble enzymes economically unviable biocatalysts in many industrial processes. Enzyme immobilization is a practical and effective method to eliminate the disadvantages of using free enzymes in industrial applications. Moreover, many enzyme properties, such as activity, selectivity, specificity, and inhibition can be tuned by immobilization. Therefore, different natural and synthetic supports have been used for the immobilization of proteases (El-Shazly et al., 2024; Katić et al., 2024; Santos et al., 2024; Ungaro et al., 2024).

The use of polyvinyl alcohol (PVA) for the immobilization of enzymes and/or proteins by entrapment has been popular in recent years because of some advantages of this technique, such as ease of immobilization, low cost, protection the 3D structure of the enzyme from pH and temperature changes, and high protein loading (Toprak et al., 2021). Fernandes et al. (2009) reported that entrapped inulinase displayed high operational stability after 20 consecutive uses at 50°C. Toprak et al. (2021) entrapped nitrilase in PVA hydrogel and showed that 80% activity recovery and 100% immobilization yield were obtained. Alagöz et al. (2022) entrapped ene reductase in PVA hydrogel and demonstrated that entrapped ene reductase had 34.4-fold higher thermal stability than free ene reductase at 30°C.

In this study, a protease derived from *Bacillus* sp. was successfully entrapped in polyvinyl alcohol (PVA) hydrogel, and both free and entrapped forms of the enzyme were extensively characterized. The reuse stability of PVA@protease was evaluated for casein hydrolysis in a batch reactor.

Materials and methods

Materials

Protease from *Bacillus* sp., casein, polyvinyl alcohol, Folin Ciocalteu's phenol reagent, glutaraldehyde (50%, w/w), and trichloroacetic acid were purchased from Sigma-Aldrich Chemie GmbH (Germany). All other chemicals were of analytical grade.

Protease immobilization

The entrapment of protease in PVA hydrogel was performed as described by Toprak et al. (2021). Before protease immobilization, 10 g of solid PVA was added to 80 mL of distilled water, and the mixture was heated to 95°C to melt the solid PVA. The mixture was then cooled to room temperature. For the entrapment of protease, 2 mL of PVA solution and one 1 mL of protease solution (1 mg protein/mL at pH 8.0) were mixed. Subsequently, 100 µL of sample was carefully dripped onto the surface of a polystyrene plate. The plates were then placed in a ventilated evaporator for 24 hours

at 5°C. The entrapped protease samples (PVA@protease) were stored at 5°C until use. The amount of protein encapsulated in PVA hydrogel was determined as described by Lowry et al. (1951). The immobilization yield and recovered activity values were calculated according to Tülek et al. (2021).

Determination of protease activity

Protease activity was measured as described by Abdella et al. (2023). A 1% (w/v) casein solution was prepared in a 50 mM Tris-HCl buffer at pH 8.0. Subsequently, 0.5 mL of the casein solution was taken and incubated in a water bath at 50 °C for 1 min. The reaction was initiated by adding 50 µL of the protease solution with a concentration of 1 mg/mL. After a 5 min reaction time, 1.5 mL of TCA (10% m/v) solution was added to terminate the reaction. The mixture was then centrifuged at 10,000 x g for 15 minutes at room temperature to separate the precipitated casein from the supernatant. The absorbance of clear supernatant was measured spectrophotometrically at 280 nm.

Optimum pH and temperature

To determine the optimum pH for both free protease and PVA@protease, activity measurements were conducted using various buffer solutions across a pH range of 5.0 to 9.0. The buffers used were 100 mM acetate (pH 5.0 and 5.5), 100 mM citrate (pH 6.0), 100 mM phosphate (pH 6.5, 7.0, 7.5 and 8.0), 100 mM Tris-HCl (pH 8.5) and 100 mM borate (pH 9.0). For each pH condition, the enzyme activity was measured, with the highest recorded activity being set as 100%, and the activities at other pH levels calculated as relative values. In addition, the optimum temperature for each protease preparation was assessed by measuring their activity over a temperature range of 40°C to 70°C, maintaining pH 8.0. Similar to the pH optimization, the highest activity observed at any temperature was designated as 100%, with all other activities expressed as relative percentages.

Thermal stability

The free protease and PVA@protease were incubated in a buffer solution without substrate at 55°C to evaluate their thermal stability over time. The residual activity of each preparation was measured at specified time intervals, with the activity at zero time considered as 100%. The residual activities were then calculated relative to this initial activity. The deactivation constant (k_d), half-life time ($t_{1/2}$) and stabilization factor (SF) of each preparation were determined as described by Tülek et al. (2021).

Kinetic parameters

The activity of both free protease and PVA@protease was evaluated across a range of casein concentrations (2-40 mg/mL) to determine the apparent Michaelis–Menten constant (K_m) and maximum reaction velocity (V_{max}) for each enzyme preparation. The measurements were performed under the optimal conditions established for each protease form. To analyze the data and estimate K_m and V_{max} values, a Lineweaver and Burk plot was used.

Reuse stability

Reuse stability of PVA@protease was carried out in a batch reactor (1.1x5 cm) at the determined optimum pH and temperature. After each cycle, the PVA@protease was washed with distilled water and these processes were repeated 5 times.

Results and discussion

In this study, a protease from *Bacillus* sp. was encapsulated in PVA hydrogels and the immobilization yield and recovered activity values were determined to be 100% and 90%, respectively. Sinha

and Khare (2015) reported the immobilization yield was 15% for *Bacillus* sp. EMB9 protease was immobilized on silica nanoparticles by simple adsorption. When silica nanoparticles were activated by glutaraldehyde, the immobilization yield increased to 40%. Thakrar and Singh (2019) encapsulated protease from *Nocardiopsis alba* TATA-5 in calcium alginate and determined the immobilization yield and recovered activity values were 96.6% and 44.8%, respectively.

The changes in the activities of free protease and the PVA@protease with increasing pH were investigated in different buffer solutions in the pH range of 5.5-9.0 and the results are presented in Figure 1. Both proteases show their maximum activities at pH 8.0. As seen in Figure 1, the PVA@protease exhibits higher relative activity at pH values below and above the maximum pH. These findings indicate that the stability of the protease against pH changes increases after immobilization.

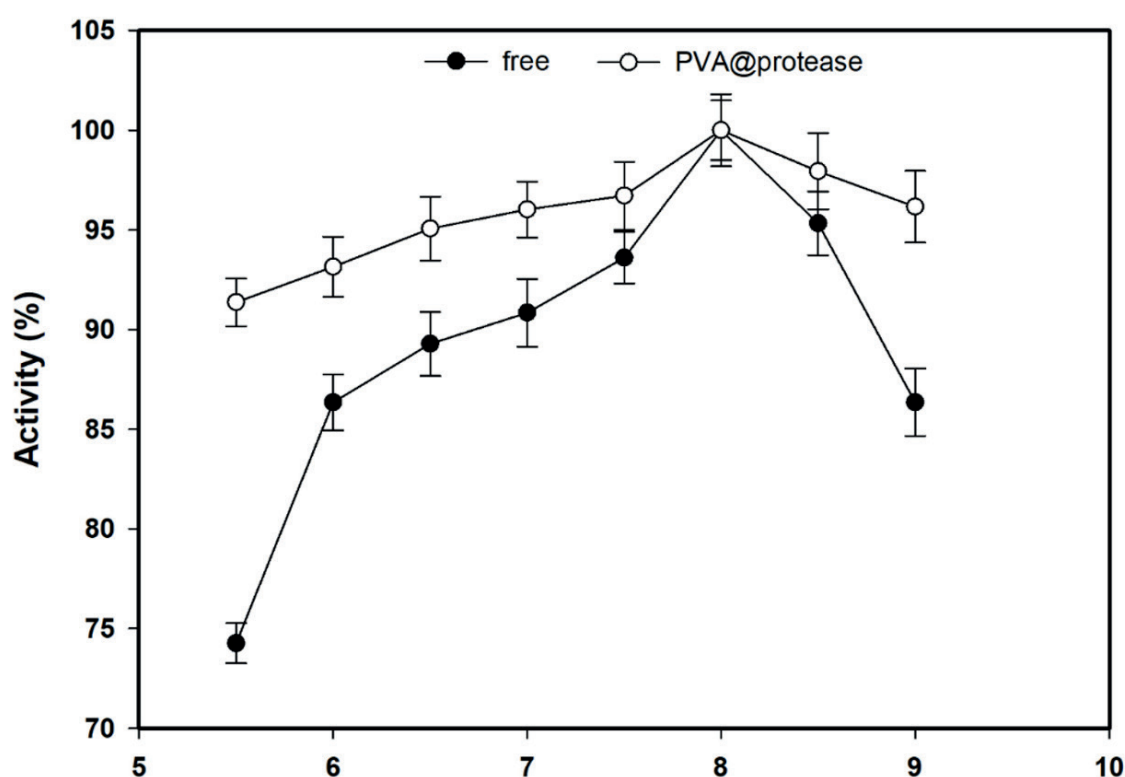


Figure 1. Effect of pH on the activity of free protease and PVA@protease at 55 °C.

The activity change of free and immobilized protease against temperature was measured at pH 8.0 in the range of 40-70°C and the results are given in Figure 2. Both free protease and the PVA@protease showed their maximum activity at 55°C. Free protease and the PVA@protease displayed almost similar relative activity values in the range of 40-55°C, while the PVA@protease demonstrated higher relative activity values than free protease at 65°C and 70°C. This indicates that the resistance of the PVA@protease increased to denaturation at 65°C and 70°C.

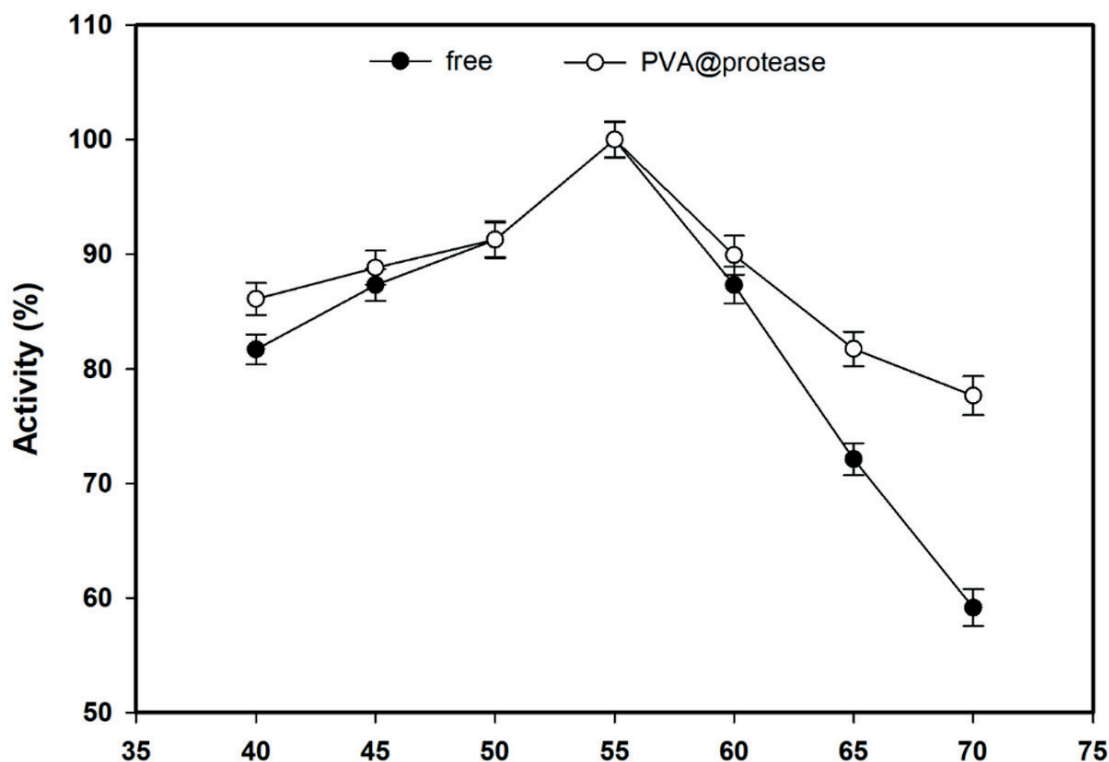


Figure 2. Effect of temperature on the activity of free protease and PVA@protease at pH 8.0.

Ferreira et al. (2003) immobilized *Bacillus licheniformis* protease onto 3-APTES-activated silica supports via glutaraldehyde spacer and found the optimum pH and temperature values as 8.0 and 60°C for both free and immobilized enzymes, respectively. Nakashima et al. (2006) reported the optimum pH value as 8.0 for free *B. licheniformis* protease. Anwar et al. (2009) immobilized *B. subtilis* protease in calcium alginate gel and found the optimum pH and temperature values 7.5 and 50°C for both the free and immobilized protease, respectively. Sinha and Khare (2015) covalently immobilized *Bacillus* sp. protease onto silica nanoparticles and determined the optimum pH and temperature as 9.0 and 55°C for both enzymes, respectively. Ramalho and de Castro (2023) determined the optimum pH and temperature values for both *B. licheniformis* protease immobilized on free and glutaraldehyde-modified chitosan as 9.0 and 60°C, respectively.

To determine the thermal stability of the free protease and the PVA@protease, the remaining activities of the enzymes were measured for different incubation times at 55°C and the results are given in Figure 3. The activity of the free protease decreased linearly with increasing incubation time and its remaining activity was calculated as 19% at the end of the 24-hour incubation. The remaining activity was calculated as 72% for the PVA@protease under the same conditions. The results show that entrapping the protease in polyvinyl alcohol creates a protective effect against denaturation. The k_d and $t_{1/2}$ values of free protease were calculated to be $65 \times 10^{-2} \text{ h}^{-1}$ and 10.6 h, respectively (Table 1). These values correspond to $13 \times 10^{-2} \text{ h}^{-1}$ and 53.3 h for the PVA@protease. SF value was 5.0 at 55°C, showing that thermal stability of the free enzyme enhances 5.0-fold upon immobilization. Wahba (2022) indicated that *B. licheniformis* protease immobilized on functionalized gum tragacanth-agar (iBPR) protected 59.8% of its initial activity after 1 h incubation at 56°C, while

the free protease preserved only 13.80% of its initial activity under the same conditions. Ferreira et al. (2003) reported that *B. licheniformis* protease immobilized on free and 3-APTES-activated silica supports via glutaraldehyde spacer lost 50% and 10% of their initial activities after 2 h incubation at 50°C, respectively. Sinha and Khare (2015) reported that free *Bacillus* sp. EMB9 protease lost 70% of its initial activity after 12 h incubation at 70°C, and the $t_{1/2}$ value at this temperature was 3 h. However, the covalently immobilized *Bacillus* sp. EMB9 protease on silica nanoparticles lost 20% of its initial activity under the same conditions, and the $t_{1/2}$ value was 8.8 h.

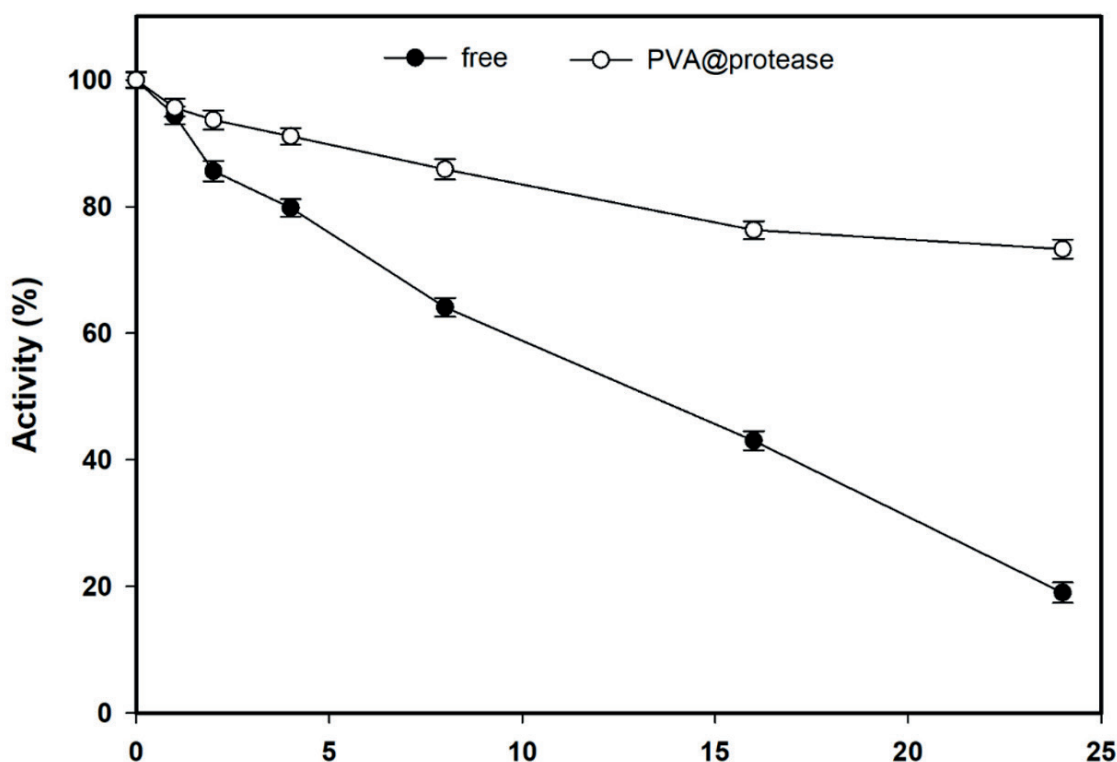


Figure 3. Thermal stability of free protease and PVA@protease at pH 8.0 and 55°C.

Table 1. Thermal stability parameters of free protease and PVA@protease at pH 8.0 and 55°C.

Enzyme form	k_d (h^{-1})	$t_{1/2}$ (h)	SF
Free protease	65×10^{-2}	10.6	-
PVA@protease	13×10^{-2}	53.3	5.0

K_m values for free protease and PVA@protease were estimated as 0.5 and 0.2 mg/mL for casein, respectively. This result indicates that the affinity of the enzyme to substrate increases 2.5-fold upon immobilization. Encapsulating the protease in PVA hydrogel may have indeed promoted proper orientation and therefore, the affinity of the protease to its substrate may have increased. The corresponding V_{max} was determined as 23.3 and 23.8 U/mg (Figure 4).


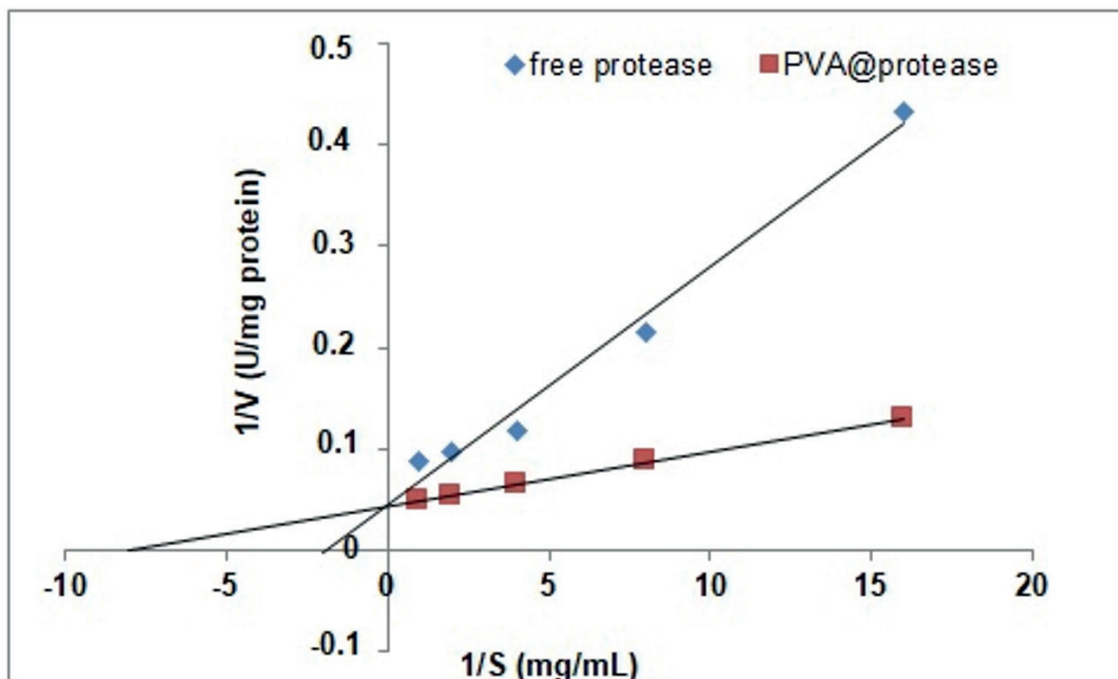


Figure 4. Lineweaver-Burk plot of free protease and PVA@protease at pH 8.0 and 55°C for different casein concentrations.

Wahba (2022) determined K_m and V_{max} values as 0.8 mg/mL and 7.8 U mg protein⁻¹, respectively for free *B. licheniformis* protease and 1.2 mg/mL and 3 U mg protein⁻¹, respectively for iBPR. Abdella et al. (2023) immobilized protease from *B. thuringiensis* on onto activated Alginate/dextrose (Alg/dex/protease) beads and reported that the K_m values of the free and Alg/dex/protease was 2.56 and 5.26 mg/mL, respectively towards casein. The corresponding V_{max} values were determined to be 121.95 and 149.52 U/mL/min. The K_m and V_{max} values of free protease from *B. pumilus* Y7 were 6.05 μ M and 20.16 U min⁻¹, respectively towards casein. These values correspond to 27 μ M and 34.13 U min⁻¹ for its entrapped counterpart in poly(vinylimidazole)/clay hydrogel. Adetunji and Olaniran (2023) reported the K_m value of the free protease from *B. aryabhattai* was 2.023 mg/mL for casein, while the encapsulated protease in alginate showed a lower K_m value of 1.225 mg/mL. The corresponding V_{max} values were found to be 232.56 and 250 U/mL.

To evaluate the reuse stability of the immobilized protease, the enzyme was utilized in a batch reactor for casein hydrolysis across five successive cycles and the results are depicted in Figure 5. The PVA@protease retained 58% of its initial activity after 5 uses. Anwar et al. (2009) observed that a protease from *Bacillus subtilis* immobilized in calcium alginate gel retained only 35% of its activity after three uses. Sinha and Khare (2015) reported that a protease from *Bacillus* sp. EMB9, retained 75% of its initial activity after six uses when covalently immobilized on silica nanoparticles. Ramalho and de Castro (2023) reported that *B. licheniformis* protease immobilized on glutaraldehyde-modified chitosan retained 47% of its initial activity after 3 uses. The iBPR remained 37.6 % of its initial activity after 10 reuses (Wahba, 2022). Thakrar and Singh (2019) demonstrated that the protease encapsulated in alginate beads preserved 85% of its initial activity after 10 successive uses. Duman and Tekin (2020) immobilized protease from *B. pumilus* Y7 in poly(vinylimidazole)/clay hydrogel and showed the immobilized protease lost 35% of its initial activity after six cycles.

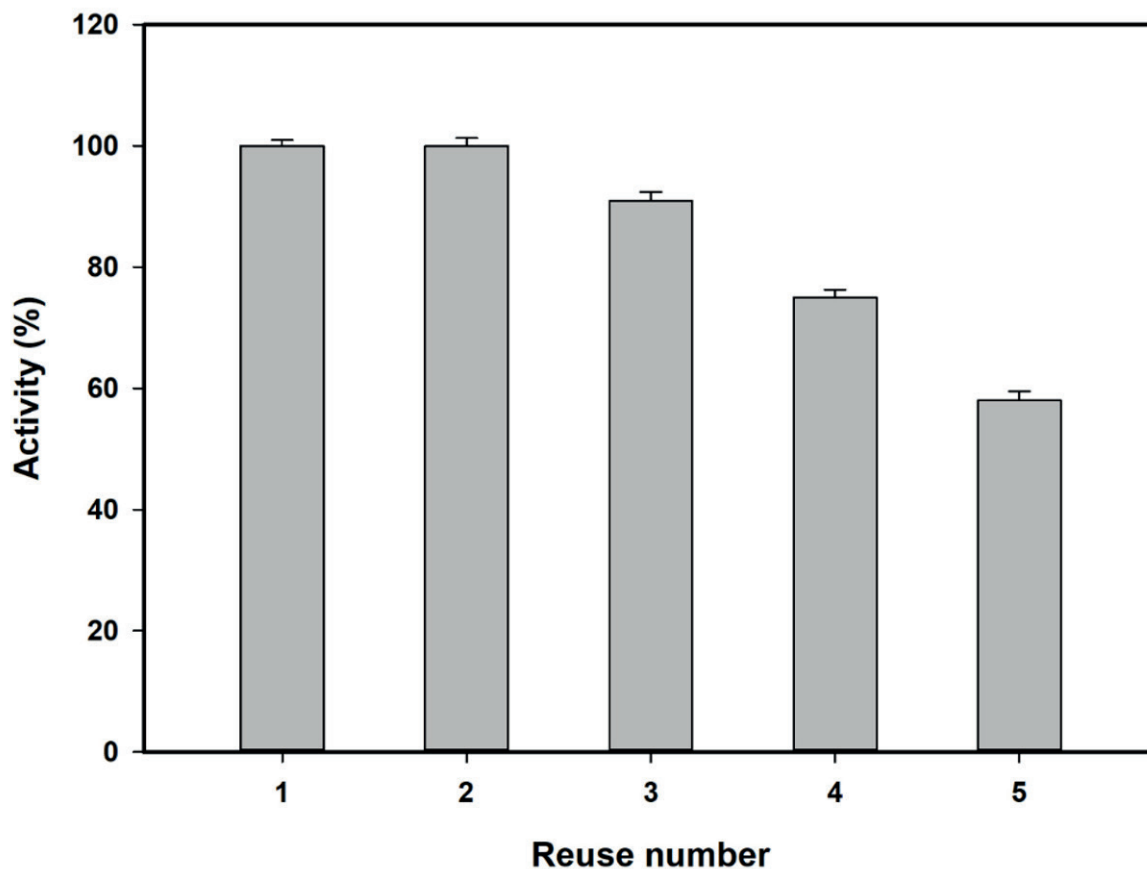

| Figure 5. Reuse stability of PVA@protease.

Conclusions

In this study, a protease from *Bacillus* sp. was successfully immobilized in PVA hydrogels. The free and PVA@protease were then characterized. Both the protease preparations showed their optimal activities at pH 8.0 and 55°C. The residual activities of free and PVA@protease were found to be 19% and 72%, respectively, after 24 h of incubation at 55°C. The SF value was calculated to be 5, indicating that stability of the protease increased 5-fold by encapsulation in PVA hydrogel at 55°C. PVA@protease protected 58% of its initial activity after 5 uses. In conclusion, entrapment of the protease in PVA hydrogels is indeed a straightforward and effective method due to mild immobilization conditions. Because PVA is biocompatible, the PVA@protease can be used in the preparation of protein hydrolyzates for the food industry.

Acknowledgements

The authors thank Prof. Hatice Korkmaz Güvenmez for her valuable comments on the manuscript.

Funding

This research was funded by Scientific Research Unit of Cukurova University (project no. FYL-2022-14813).

Conflict of interest

The authors declare that there is no conflict of interest regarding the publication of this study.

Data availability statement

Additional information, data, or materials related to the study can be provided from the corresponding author upon reasonable request.

Ethics committee approval

This research does not involve human participants, animals, or sensitive data.

Authors' contribution statement

The authors acknowledge their contributions to this paper as follows: **Experiment design:** D.Y.; **Data collection:** F.M.H.; **Analysis of data:** F.M.H. and D.Y.; **Manuscript writing:** F.M.H. and D.Y. all authors agree with the findings and conclusions presented in the manuscript.

ORCIDs and emails of the authors

Fatih Mehmet Hasbek | ORCID 0009-0000-4780-9745 | fmh58343133.af@gmail.com

Deniz Yildirim | ORCID 0000-0002-5041-8160 | dyildirim@cu.edu.tr

References

- Abdella, M. A. A., Ahmed, S. A., & Hassan, M. E. (2023). Protease immobilization on a novel activated carrier alginate/dextrose beads: Improved stability and catalytic activity via covalent binding. *International journal of biological macromolecules*, 230, 123139. <https://doi.org/10.1016/j.ijbiomac.2023.123139>
- Adetunji, A. I., & Olaniran, A. O. (2023). Biocatalytic profiling of free and immobilized partially purified alkaline protease from an autochthonous *Bacillus aryabhatai* Ab15-ES. *Reactions*, 4(2), 231-245. <https://doi.org/10.3390/reactions4020013>
- Alagöz, D., Varan, N. E., Toprak, A., Tükel, S. S., & Yildirim, D. (2022). Immobilization of ene reductase in polyvinyl alcohol hydrogel. *Protein journal*, 41, 394–402. <https://doi.org/10.1007/s10930-022-10059-4>
- Anwar, A., Qader, S. A. U., Raiz, A., Iqbal, S., & Azhar, A. (2009). Calcium alginate: A support material for immobilization of proteases from newly isolated strain of *Bacillus subtilis* KIBGE-HAS. *World applied sciences journal*, 7(10), 1281-1286.
- Brandelli, A., & Daroit, D. J. (2024). Unconventional microbial proteases as promising tools for the production of bioactive protein hydrolysates. *Critical reviews in food science & nutrition*, 64(14), 4714-4745. <https://doi.org/10.1080/10408398.2022.2145262>
- Duman, Y. A., & Tekin, N. (2020). Kinetic and thermodynamic properties of purified alkaline protease from *Bacillus pumilus* Y7 and non-covalent immobilization to poly(vinylimidazole)/clay hydrogel. *Engineering in life sciences*, 20, 36-49. <https://doi.org/10.1002/elsc.201900119>
- Dyer, R. P., & Weiss, G. A. (2022). Making the cut with protease engineering. *Cell chemical biology*, 29(2), 177-190. <https://doi.org/10.1016/j.chembiol.2021.12.001>

- Elbira, A., Hafiz, M., Hernández-Álvarez, A. J., Zulyniak, M. A., & Boesch, C. (2024). Protein hydrolysates and bioactive peptides as mediators of blood glucose-A systematic review and meta-analysis of acute and long-term studies. *Nutrients*, 16(2), 323. <https://doi.org/10.3390/nu16020323>
- El-Shazly, A. I., Wahba, M. I., Abdelwahed, N. A. M., & Shehata, A. N. (2024). Immobilization of alkaline protease produced by *Streptomyces rochei* strain NAM-19 in solid state fermentation based on medium optimization using central composite design. *3 Biotech*, 14, 161. <https://doi.org/10.1007/s13205-024-04003-9>
- Ferreira, L., Ramos, M. A., Dordick, J. S., & Gil, M. H. (2003). Influence of different silica derivatives in the immobilization and stabilization of a *Bacillus licheniformis* protease (Subtilisin Carlsberg). *Journal of molecular catalysis b: Enzymatic*, 21, 189-199. [https://doi.org/10.1016/S1381-1177\(02\)00223-0](https://doi.org/10.1016/S1381-1177(02)00223-0)
- Fernandes, P., Marques, M. P. C., Carvalho, F., & Cabral, J. M. S. (2009). A simple method for biocatalyst immobilization using PVA-based hydrogel particles. *Journal of chemical technology & biotechnology*, 84, 561-564. [https://doi.org/10.1016/S1381-1177\(02\)00223-0](https://doi.org/10.1016/S1381-1177(02)00223-0)
- Katić, K., Banjanac, K., Simović, M., Veljković, M., Ćorović, M., Denić, L., Zakić, T., Kralj, S., & Bezbradica, D. (2024). Nanobiocatalyst based on covalent immobilization of proteases onto functionalized nanocellulose for efficient production of sunflower meal protein hydrolysates. *Food bioscience*, 61, 104590. <https://doi.org/10.1016/j.fbio.2024.104590>
- Lowry, O. H., Rosebrough, N. J., Farr, A. L., & Randall, R. J. (1951). Protein measurement with the Folin phenol reagent. *Journal of biological chemistry*, 193, 265-275. [https://doi.org/10.1016/S0021-9258\(19\)52451-6](https://doi.org/10.1016/S0021-9258(19)52451-6)
- Nakashima, K., Maruyama, T., Kamiya, N., & Goto, M. (2006). Homogeneous enzymatic reactions in ionic liquids with poly(ethylene glycol)-modified subtilisin. *Organic & biomolecular chemistry*, 4, 3462-3467. <https://doi.org/10.1039/b608920h>
- Ramalho, E. X., & de Castro, R. J. S. (2023). Covalent bonding immobilization of a *Bacillus licheniformis* protease on chitosan and its application in protein hydrolysis. *Biocatalysis & agricultural biotechnology*, 50, 102713. <https://doi.org/10.1016/j.bcab.2023.102713>
- Santos, M. P. F., de Souza Junior, E. C., Villadóniga, C., Vallés, D., Castro-Sowinski, S., Bonomo, R. C. F., & Veloso, C. M. (2024). Proteases: Importance, immobilization protocols, potential of activated carbon as support, and the importance of modifying supports for immobilization. *Biotech*, 13(2), 13. <https://doi.org/10.3390/biotech13020013>
- Sinha, R., & Khare, S. K. (2015). Immobilization of halophilic *Bacillus* sp. EMB9 protease on functionalized silica nanoparticles and application in whey protein hydrolysis. *Bioprocess & biosystems engineering*, 38, 739-748. <https://doi.org/10.1007/s00449-014-1314-2>
- Sun, W., Shahrajabian, M. H., Kuang, Y., & Wang, N. (2024). Amino acids biostimulants and protein hydrolysates in agricultural sciences. *Plants*, 13(2), 210. <https://doi.org/10.3390/plants13020210>
- Tang, T., Wu, N., Tang, S., Xiao, N., Jiang, Y., Tu, Y., & Xu, M. (2023). Industrial application of protein hydrolysates in food. *Journal of agricultural & food chemistry*, 71(4), 1788-1801. <https://doi.org/10.1021/acs.jafc.3c00000>

doi.org/10.1021/acs.jafc.2c06957

- Thakrar, F. J., & Singh, S. P. (2019). Catalytic, thermodynamic and structural properties of an immobilized and highly thermostable alkaline protease from a haloalkaliphilic actinobacteria, *Nocardopsis alba* TATA-5. *Bioresource technology*, 278, 150-158. <https://doi.org/10.1016/j.biortech.2019.01.058>
- Toprak, A., Tükel, S. S., & Yildirim, D. (2021). Stabilization of multimeric nitrilase via different immobilization techniques for hydrolysis of acrylonitrile to acrylic acid. *Biocatalysis & biotransformation*, 39(3), 221–231. <https://doi.org/10.1080/10242422.2020.1869217>
- Tülek, A., Yildirim, D., Aydın, D., & Binay, B. (2021). Highly-stable *Madurella mycetomatis* laccase immobilized in silica-coated ZIF-8 nanocomposites for environmentally friendly cotton bleaching process. *Colloids & surfaces b: Biointerfaces*, 202, 111672. <https://doi.org/10.1016/j.colsurfb.2021.111672>
- Ungaro, V. A., Fairbanks, J. P. A., Rossi, L. M., & Machini, M. T. (2024). Fe₃O₄@silica-thermolysin: A robust, advantageous, and reusable microbial nanobiocatalyst for proteolysis and milk-clotting. *International journal of biological macromolecules*, 278(1), 134503. <https://doi.org/10.1016/j.ijbiomac.2024.134503>
- Wahba, M. I. (2022). Gum tragacanth for immobilization of *Bacillus licheniformis* protease: Optimization, thermodynamics and application. *Reactive & functional polymers*, 179, 105366. <https://doi.org/10.1016/j.reactfunctpolym.2022.105366>